




High Performance Paint Specification

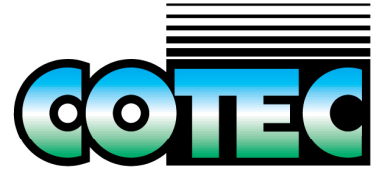

PS-E009

COATING METALS WITH EPOTEC HB EPOXY PAINT

INTRODUCTION:

EPOTEC High Build Epoxy is a functional epoxy coating very suitable for protecting metals from chemicals or aggressive environments. Like all specifications for metals it is important to have a primer which has either anticorrosive or sacrificial anodic protection.

PROCEDURE:

STEEL:

- (a) Heavy gauged structural components:
 - 1 Grit blast to SA 2.5.
 - 2 Zinc rich inorganic/organic primer.
 - 3 Two coats of EPOTEC High Build Epoxy.

- (b) Light gauged steel sheet:
 - 1 Remove all rust by abrading or light blasting. Any remaining light rusting can be treated with a suitable rust killing solution (phosphoric or Tannic acid type) by rag or brush. Steel wool can be used to scour the surface rust.

For use in more corrosive environment:

- 2 Zinc rich inorganic/organic primer.
- 3 Two coats of EPOTEC High Build Epoxy.

For use in less corrosive (not marine or chemical) environments:

- 1 Remove rust as above.
- 2 Apply a coat of TUFF COTE DTM (anti corrosive) PRIMER.
- 3 Apply 2 coats of Epotec High Build Epoxy.

GALVANISED IRON (HOT DIPPED OR SPANGLE):

- 1 Apply solution zinc phosphate to surface. Preparation instructions need to be followed, or wash with a Phosphoric based metal treatment solution such as RUSTKILL.

- 2 Apply a coat of EPS-10 ETCH PRIMER, or TUFF COTE DTM PRIMER. Brush or spray applied.

- 3 Two coats of EPOTEC High Build Epoxy. Brush applied.

PTO

Coating Technologies Limited, 16 Aetna Place, Henderson, Auckland, New Zealand

Phone: 0064 9 837 0897 Fax: 0064 9 837 3736 www.cotec.co.nz

Technical information given verbally or in writing is based on knowledge and research, given in good faith and believed to be reliable, but no guarantee of accuracy is made or implied. Since methods and conditions of use are beyond our control, all merchandise is sold and received subject to the condition that our liability whether express or implied for any defect in quality, or for any lack of fitness for the specified use thereof, is limited to the return of the purchase price if written claim is made within 14 days from the date of delivery. It is recommended that the user makes his or her own tests to determine the suitability of the product for his own requirements. Freedom from patent restrictions is not implied.

ALUMINIUM:

- 1 Degrease surface with suitable solvent cleaner. E.g. Isopropyl alcohol. For best adhesion aluminium should be cleaned with a proprietary preparation system such as (Ridolean 1509 ALX followed by a conversion coating Alodine 1000L).
- 2 EPS-10 ETCH PRIMER. Brush or spray applied or TUFF COTE DTM PRIMER brush or spray applied.
- 3 Two coats of EPOTEC High Build Epoxy. Brush applied.

For specific recommendations of products refer to Coating Technologies Limited's technical department.

APPLICATION OF EPOTEC HIGH BUILD EPOXY (GENERAL):

MIX CAREFULLY the Epotec High Build Epoxy pack. The steps being: Add the hardener (500 grams) to the base can (2.5kgs in the 4 litre Base can). Using a flat stick mix well – Taking particular care to mix in the sides and bottom. Do not induce air bubbles into mix. Allow to stand for 10 minutes. Re-mix briefly. A good idea when a large number of units requires mixing is to write with a marker pen the time when ready for use

POT LIFE:

This is the approximate time you have before the mixed material becomes unworkable. This time will vary depending on the colour, ambient temperature and the relative humidity on the day. Approximate times are:

15°C	Ambient	3 – 4 hours
25°C	Ambient	1 – 2 hours.

HEALTH AND SAFETY:

Read the Material Safety Data Sheet (MSDS) and information booklet. Keep away from heat and open flames, keep can closed when not in use. Avoid breathing vapour, use with adequate ventilation. Avoid contact with skin and eyes. If skin contact occurs use warm soapy water to remove. Do NOT use thinner to clean the skin.

ISSUE: 03 DATE: 1/12/13